

JIPK

(JURNAL ILMIAH PERIKANAN DAN KELAUTAN)



Scientific Journal of Fisheries and Marine

Short Communication

The Characteristics of Chitosan Derived from Lobster Shells and its Effect on Fungi Activity and Water Stability of Lobster Pellets

Muhsinul Ihsan^{1*}, Ali Harris¹, Mukminah¹, Megawati¹, Nining Purwati¹, Handa Muliasari², Bayu Priyambodo³, Clive Jones⁴, and Leo Nankervis⁴

¹Department of Biology Education, Faculty of Teacher and Training, Universitas Islam Negeri Mataram. Indonesia

²Department of Pharmacy, Faculty of Medicine and Health Sciences, University of Mataram. Indonesia

³Lombok Marine Aquaculture Development Centre. Indonesia

⁴Centre for Sustainable Tropical Fisheries and Aquaculture, James Cook University. Australia



ARTICLE INFO

Received: May 10, 2024
Accepted: Jan 31, 2025
Published: Feb 17, 2025
Available online: May 25, 2025

*) Corresponding author:
E-mail: ihsan@uinmataram.ac.id

Keywords:

Chitosan Extraction
Lobster Feed Stability
Anti-fungal
Coating
Pellet



This is an open access article under the CC BY-NC-SA license (<https://creativecommons.org/licenses/by-nc-sa/4.0/>)

Abstract

Tropical rock lobster aquaculture is a lucrative industry that is currently limited by the lack of appropriate formulated feed. Its nocturnal, benthic feeding behavior necessitates a water-stable feed that maintains integrity under tropical marine conditions without degrading. Chitosan, a biopolymer derived from lobster (*Panulirus homarus*) shells, has potential applications in aquaculture as an antifungal agent and feed binder. We report on the characteristics of chitosan extracted from the exoskeleton of spiny lobsters (*Panulirus homarus*), including its effect on fungal activity and water stability of pellets. Chitosan was produced through three main steps: deproteination, demineralization, and deacetylation. The resulting chitosan was characterized through crude composition (AOAC methods), FTIR spectra, and scanning electron microscope (SEM), while anti-fungal activity was assessed through *in vitro* assays. Chitosan was used to coat lobster feed pellets by immersion method at different concentrations (0%, 0.5%, 1%, 1.5%, and 2%), and its impact on pellet water stability was assessed. There were three replications in fungal activity and water stability test. The yield of chitosan was $5.9 \pm 0.01\%$ of the total shell mass, with $96.99\% \pm 0.01$ degree of deacetylation (DD). The resulting product contained $5.94 \pm 0.07\%$ moisture, $36.72 \pm 0.05\%$ ash and $2.73 \pm 0.08\%$ nitrogen. Chitosan morphology was characterized as an irregular shape with dimensions ranging from 157 to 391 μm , with a combination of striated surface textures. Increasing concentration of chitosan increased water stability of pellets up to 1.5% inclusion, while 0.5% optimized *Fusarium* sp. inhibition. These findings suggest that chitosan from lobster shells can be sustainably utilized to enhance feed quality, reducing fungal contamination and nutrient leaching in aquaculture systems.

Cite this as: Ihsan, M., Harris, A., Mukminah., Megawati., Purwati, N., Muliasari, H., Priyambodo, B., Jones, C., & Nankervis, L. (2025). The Characteristics of Chitosan Derived from Lobster Shells and its Effect on Fungi Activity and Water Stability of Lobster Pellets. *Jurnal Ilmiah Perikanan dan Kelautan*, 17(2):485–497. <https://doi.org/10.20473/jipk.v17i2.57474>

1. Introduction

The Spiny Lobster (*Panulirus homarus*) is amongst the highest value seafood products, and has become the basis of a rapidly expanding aquaculture industry in Indonesia (Jones et al., 2019). In 2021, Indonesia exported around 1.96 thousand tons of lobsters, with value 28.62 million USD (Statista, 2024). This production industry has resulted in higher quantities of lobster consumption, and resultant higher volume of waste shells, which pose a disposal issue. These shells are currently disposed of in municipal waste. However, they pose an opportunity for co-product development to add circularity to the lobster supply chain, reducing waste and pollution.

Chitin is the main component in the shells of crustaceans such as shrimp, crab, squid, crayfish, and lobster. It is also can be found in the exoskeleton of mollusks and insects as well as in the cell of walls of some fungi. The derivative of chitin is chitosan. Both of them are natural polysaccharides which contain two monosaccharides, *N*-acetyl *D*-glucosamine and *D*-glucosamine, connected by β -1,4-glycoside bonds. Chitin consists of mainly *N*-acetyl *D*-glucosamine, while chitosan contains mainly *D*-glucosamine (Bastiaens et al., 2020). The presence of primary and secondary hydroxyl groups and the amine groups in each deacetylated unit make chitosan chemically more active than chitin (Amine et al., 2021). These properties have made chitosan a promising candidate for multiple applications, particularly as an antimicrobial and coating agent in food preservation and aquafeed formulations.

The bioactivity of chitosan is defined as its ability to interact with other compounds, pathogens, or microorganisms. Chitosan and its derivatives can be used as a coating agent and are effective against pathogen in foodstuff (Betchem et al., 2019; Chaudhari et al., 2023; Chouhan and Mandal, 2021; Confederat et al., 2021; Díaz-montes and Castro-muñoz, 2021; Divya et al., 2018; Karamchandani et al., 2022; Li and Zhuang, 2020; Picos-Corrales et al., 2023; Román-Doval et al., 2023; Romanazzi et al., 2018; Romanazzi and Mounni, 2022; Shahbaz et al., 2023; Shrestha et al., 2023; Teixeira-Santos et al., 2021; Zeng et al., 2021). Furthermore, in aquaculture, chitosan and its derivatives also have positive effects against pathogen in *Oreochromis niloticus* (Abdel-Razek, 2019; Aly et al., 2023; Elbahnaswy et al., 2021; Fadl et al., 2020; Ibrahim et al., 2021; Naiel et al., 2020; Shi et al., 2020; Xu et al., 2023), *Barbonymus gonionotus* (Salam et al., 2021), sea cucumber *Apostichus japonicus* (Wang et al., 2023), tropical rohu fish, *Labeo rohita* (Kumar et al., 2022),

and Hybrid grouper (*Epinephelus fuscoguttatus* ♀ × *E. lanceolatus* ♂) (Chen et al., 2021).

Besides its tremendous effects as an antimicrobial, chitosan also improves the physical properties of pellets. Previous studies revealed that chitosan-coated microdiet improves significantly water stability and retains more nutrients of feed of *Machrobrachium rosenbergii* (Anas et al., 2008), olive flounder, *Paralichthys olivaceus*, (Cha et al., 2008), *Cherax albidus* (Volpe et al., 2012), and yellow croaker larvae feed (Liu et al., 2022). The ability of chitosan to form edible films is mainly due to its polycationic nature that allows it to work in conjunction with other biopolymers and additives. This synergy causes strong physical interactions between all the components, which reflects the improvement of the physical, mechanical, and permeability properties (Díaz-montes and Castro-muñoz, 2021; Saputra et al., 2022). In addition, the quality of chitosan depends on several aspects, such as concentration, the degree of deacetylation, pH, moisture content, ash, nitrogen, and the species of animals (Goy et al., 2009; Kurniawidi et al., 2022).

Based on previous studies, it can be seen that chitosan has been studied widely as an antimicrobial and an edible coating in foodstuff and artificial feed of aquaculture animals. In addition, some studies also reported the quality of chitosan from several animals. However, there is little information in terms of the quality of chitosan from lobster shells of *Panulirus homarus* and its effects on the lobster feed (pellets). This study aims to measure the quality of chitosan derived from lobster shells of *Panulirus homarus*, and observe its effects on the fungi activities in pellets and water stability of lobster pellets.

2. Materials and Methods

2.1 Materials

2.1.1 The equipments

The research equipments were magnetic stirrer (Guardian 7000 G71HS10C HPS 18 L Hotplate Stirrer - IC-30500611), FTIR spectrophotometer (Nicolet iS50, Thermo Fisher Scientific, Australia), scanning electron microscope, energy-dispersive X-ray spectroscopy (SEM-EDX) (JCM-7000 Benchtop SEM, JEOL, USA), horizontal water bath shaker (Fisherbrand™ Isotemp™, Fisher Scientific, USA), and oven (ESCO scientific, Isotherm® Forced Convection Lab Oven). All of these equipments were provided by the Immunobiology Laboratory, Universitas Mataram and Integrated Laboratory, Universitas Islam Negeri Mataram.

2.1.2 The materials

About 1000 g of Spiny Lobster (*Panulirus homarus*) shells were collected from the lobster aquaculture center in Jerowaru, East Lombok, Indonesia. These samples were cleaned with water and dried in an oven at 80°C for 24 hours and then mashed with 60 mesh. The reagents and chemicals were supplied by Sigma Aldrich, Singapore.

2.1.3 Ethical approval

This study does not require ethical approval because it does not use experimental animals.

2.2 Methods

2.2.1 Preparation of chitosan

The chitosan extraction process followed three key steps: deproteination, demineralization, and deacetylation, adapted from previous studies on crustacean-derived chitosan. The first step was performed using 3% NaOH solvent (1:5 w/v) at 70°C using a hot plate under continuous stirring for two hours (Masrurianti et al., 2020). The samples were washed with distilled water and dried in an oven. The demineralization was carried out using 1N HCl solvent (1:10 w/v) at 80°C using magnetic stirrer for one hour. The samples were cleaned with distilled water and dried in an oven. Chitin was successfully produced after these steps. Then, chitin was formed into chitosan through a deacetylation process using 50% NaOH in a ratio of 1:15 (chitin to NaOH solution) at 80°C with stirring for one hour. The sample was cleaned using distilled water and dried in an oven at 80°C for eight hours (Azmin et al., 2019).

2.2.2 Characterization of chitosan

The quality of chitosan was assessed by measuring the water, ash, and nitrogen content based on the standard analytical methods (Association of Official Analytical Chemists). FTIR spectrophotometer (Nicolet iS50, Thermo Fisher Scientific, Australia) was used to measure the degree of deacetylation (DD). This is calculated by comparing the absorbance at 1.655 cm⁻¹ and 3.450 cm⁻¹. The characterization of chitosan was continued by observing the morphology of chitosan using scanning electron microscope, energy-dispersive X-ray spectroscopy (SEM-EDX) (JCM-7000 Benchtop SEM, JEOL, USA). The yield percentage of chitosan was calculated by the formula:

Yield (%) = Dry Chitosan mass (g) / Dry raw material mass (g) x 100.....(1)

2.2.3 Assessment of anti-fungal activity

There were three main steps in this activity, namely: lobster feed preparation, isolation of fungi from lobster feed, and *in vitro* assays of antifungal activity of chitosan. Lobster feed preparation for *in vitro* and *in vivo* assays was based on the previous research developed by Ihsan et al. (2020) with little modification in the formula (Table 1). Fungi were isolated from lobster feed by serial dilution and spread plate method. Serial dilution (10⁻¹ and 10⁻²) was made by diluting 10 g of lobster feed in 9 mL of sterile aquadest; 0.1 mL of the suspensions were inoculated in a petri disc containing PCA (plate count agar) and incubated for seven days in room temperature. The identification of fungi was conducted by macroscopic and microscopic observation. The anti-fungal activity of chitosan was determined using diffusion-type assays. Fungi were spread in PCA media using a sterile spreader and 25 µL of chitosan solution which was produced by dissolving chitosan in an added 1% acetic acid. There were three replications and five concentrations of chitosan as treatments, namely: 0%, 0.5%, 1%, 1.5%, and 2%. The inhibition zone was measured after seven days incubation of dishes.

Table 1. Lobster feed formulation.

No	Ingredients	Formula (%/Kg)
1	Fish meal	53
2	Shrimp meal	26.4
3	Wheat	5
4	Soy meal	5
5	ISP	1
6	Fibrisol	0.005
7	Astaxanthin	0.005
8	Vitamin mix	1.4
9	Mineral mix	1
10	Fish Oil	3
11	Agar-agar powder	3.7
Total		100

2.2.4 Water stability test

The water stability test of lobster pellets was conducted through two main phases, namely coating phase and a leaching loss test phase. The pellets were

coated by chitosan using immersion method. Two grams of pellets were immersed for 60 minutes in five different chitosan solutions (0%, 0.5%, 1%, 1.5%, and 2%) as treatments with three replications. These pellets were placed in five glasses containing 100 mL of seawater and shaken by a horizontal water bath shaker (Fisher-brand™ Isotemp™, Fisher Scientific, USA) at 100 rpm for 15 minutes at 25°C. The remaining pellets were dried at 105°C for 24 hours and weighed. The physical stability of pellets in terms of dry matter retention was counted by the following formula:

$$\text{Water Stability (\%)} = \frac{\text{feed remaining (g)}}{\text{initial feed (g)}} \times 100 \dots\dots\dots(2)$$

2.3 Analysis Data

Software SPSS 25 was used to perform one-way ANOVA test, which analyzed the differentiation between the means of treatments in anti-fungal and water stability test. However, post-hoc analysis revealed no significant improvement in stability beyond 1.5% chitosan inclusion, supporting the hypothesis that excessive chitosan cross-linking reduces pellet flexibility. Tukey's test was used to identify the treatments which differ exactly from each other.

3. Results and Discussion

3.1 Results

3.1.1 Characteristics of chitosan

The yield of resulted chitosan was 5.9%, while moisture, ash, and nitrogen content were 5.94%, 36.72%, and 2.73% respectively. Degree of deacetylation (DD) was 96.99% (Table 2). The FTIR spectra of chitosan from lobster shells can be seen in Figure 1 which shows that O-H vibration is detected at band 3377.65 cm⁻¹, while 2790.75 cm⁻¹ and 2586.52 cm⁻¹ indicate the C-H stretching. The C-O stretching and N-H banding were observed at 1028.92 cm⁻¹ and 1419.01 cm⁻¹ respectively.

Table 2. Characteristics of chitosan.

Parameters	Results ± SD (%)	Standards	
		Protan Laboratory	EFSA
Yield	5.9 ± 0.01	-	-
Moisture	5.94 ± 0.07	≤ 10	≤ 10
Ash	36.72 ± 0.05	≤ 2	≤ 3
Nitrogen	2.73 ± 0.08	-	≤ 6
Degree of deacetylation (DD)	96.99 ± 0.01	≥ 70	≥ 90

The morphology of chitosan observed by scanning electron microscope is the irregular shape, 157µm – 391 µm particle size (Figure 2A). The magnification by 2000 times shows that the chitosan is striated with a rough surface (Figure 2B). Energy-dispersive X-ray spectroscopy (EDX) indicates the chitosan consist of carbon and oxygen as the constituent elements, whereas calcium, natrium, magnesium, aluminum, and phosphate are the metal impurities from lobster shells (Figure 2C).

3.1.2 Anti-fungal activity of chitosan

The fungi growing on lobster pellets in this study were identified as *Fusarium* spp. (Figure 3). The antifungal activity of chitosan can be seen in Figure 4. The lowest chitosan concentration (0.5% of chitosan) resulted in the highest zone of inhibition, with decreasing inhibition as chitosan concentration was increased further.

3.1.3 Water stability of lobster pellets

The percentage of water stability of pellets can be seen in Table 3, while the color of water changing before and after water stability test is displayed in Figure 5. Based on Table 3, there is dose-dependent increase in water stability with increasing chitosan concentration, up to 1.5%. This is supported by visual observation of leaching nutrient (Figure 5).

3.2 Discussion

3.2.1 Characteristics of chitosan

The quality of chitosan extracted from Spiny Lobster (*Panulirus homarus*) shells relies on water, ash, nitrogen, and degree of deacetylation (DD). The quality was compared with Protan Laboratory and Food Safety Authority (EFSA) as standards and is displayed in Table 2.

Based on Table 2, the yield of chitosan was slightly higher than previous research conducted by

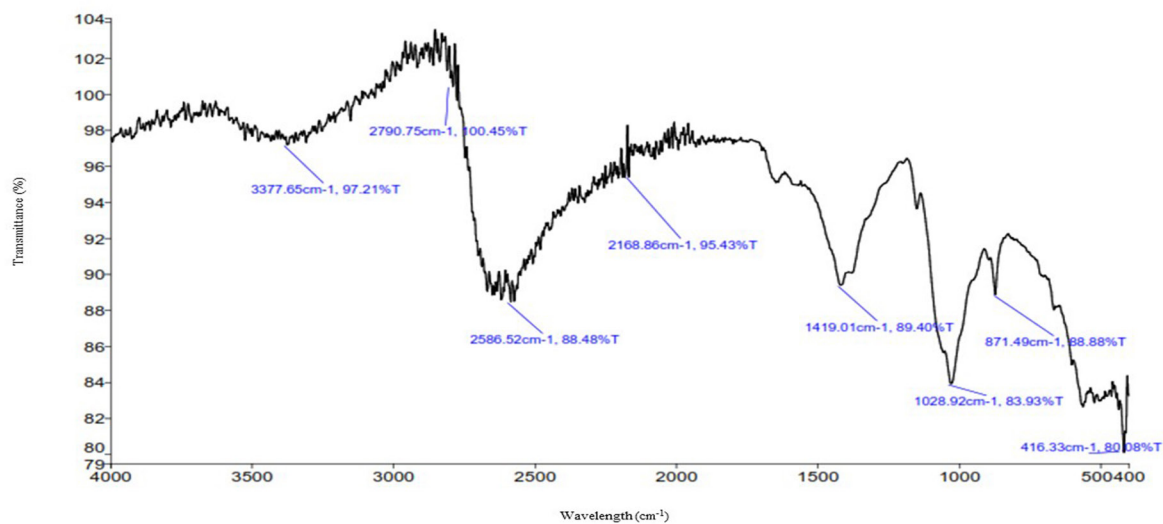


Figure 1. FTIR spectrum of the lobster shells (*Panulirus homarus*).

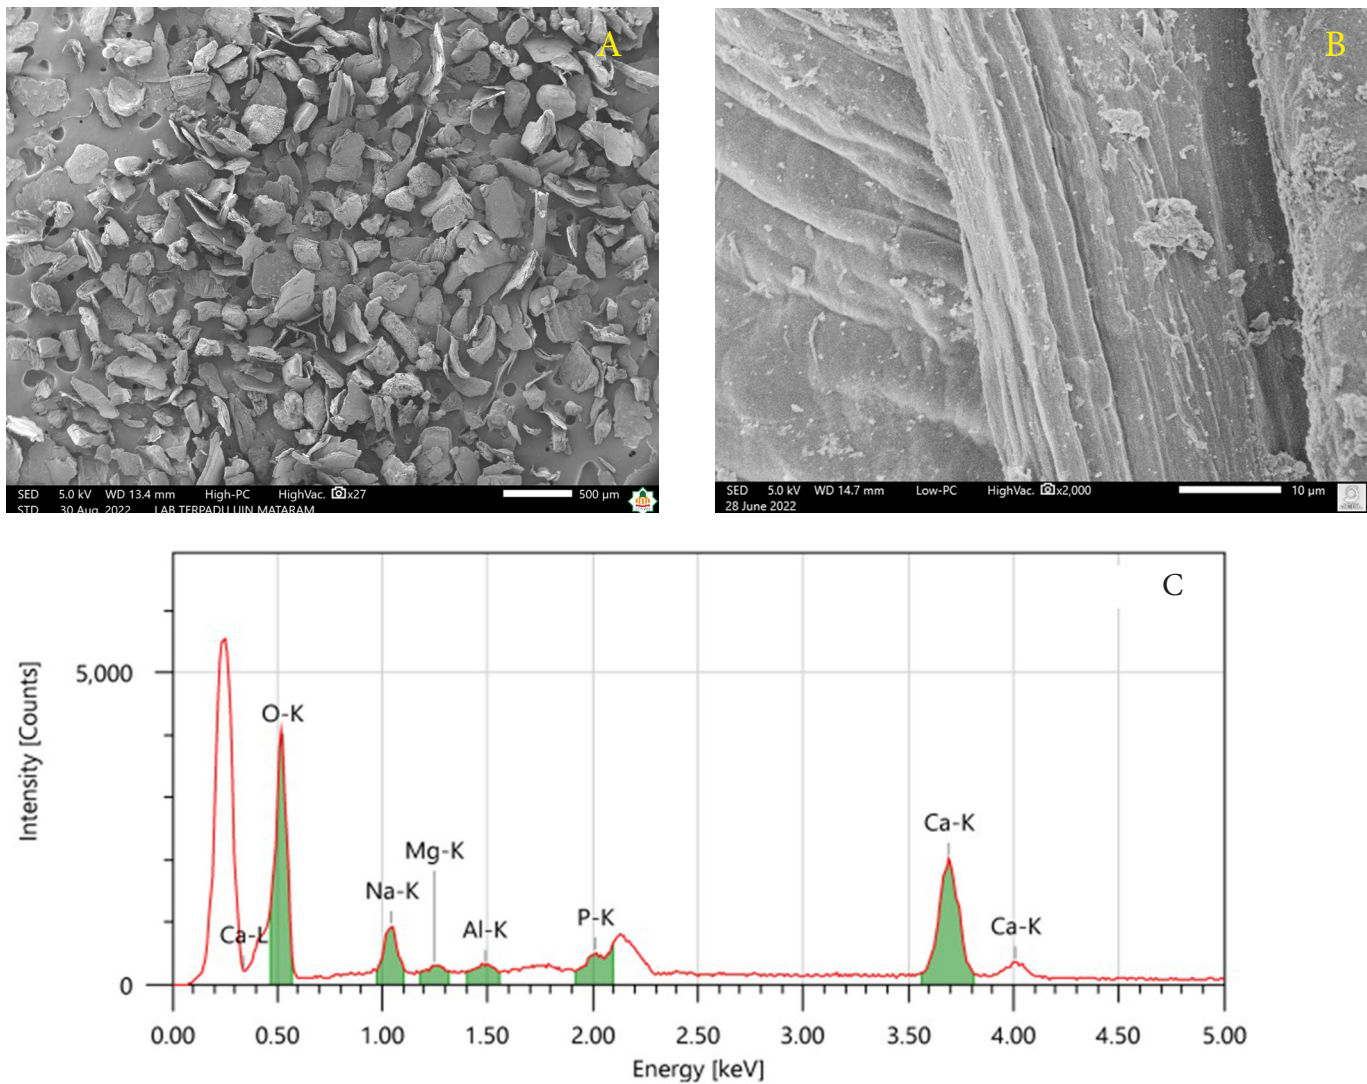


Figure 2. Scanning electron microscope-Energy Dispersive X-Ray (SEM-EDX) (A, B); composition of chitosan (C).

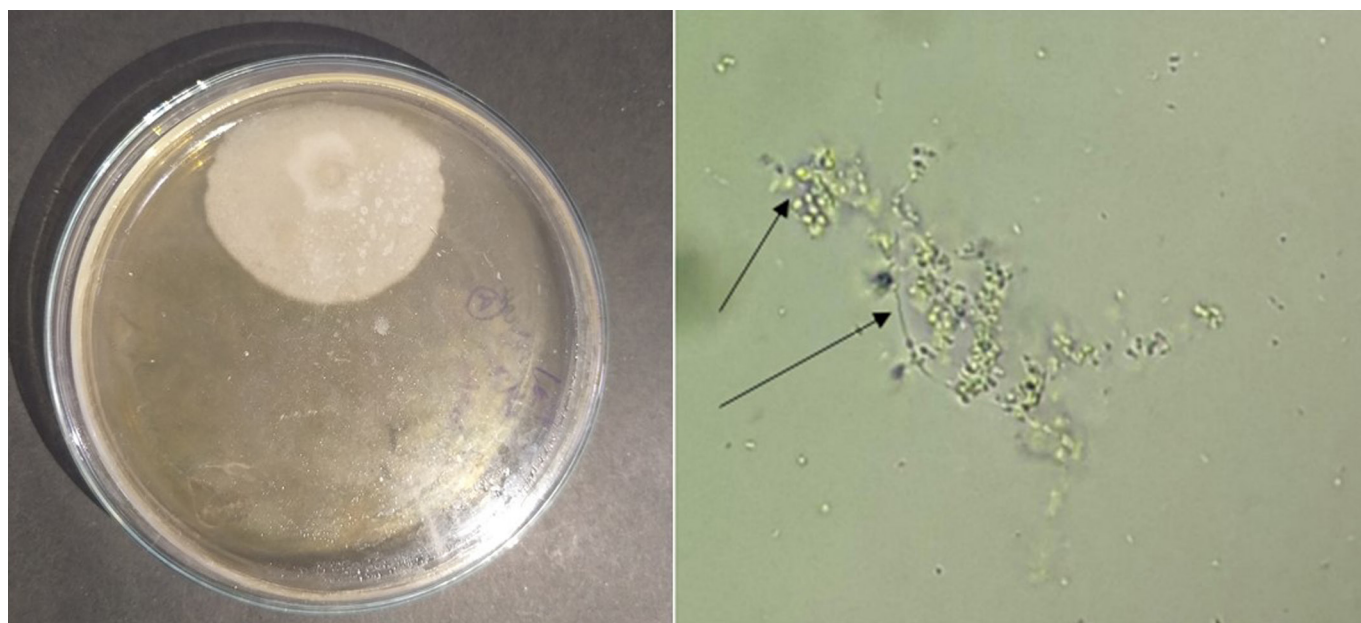


Figure 3. *Fusarium* spp. Isolated from lobster pellets.

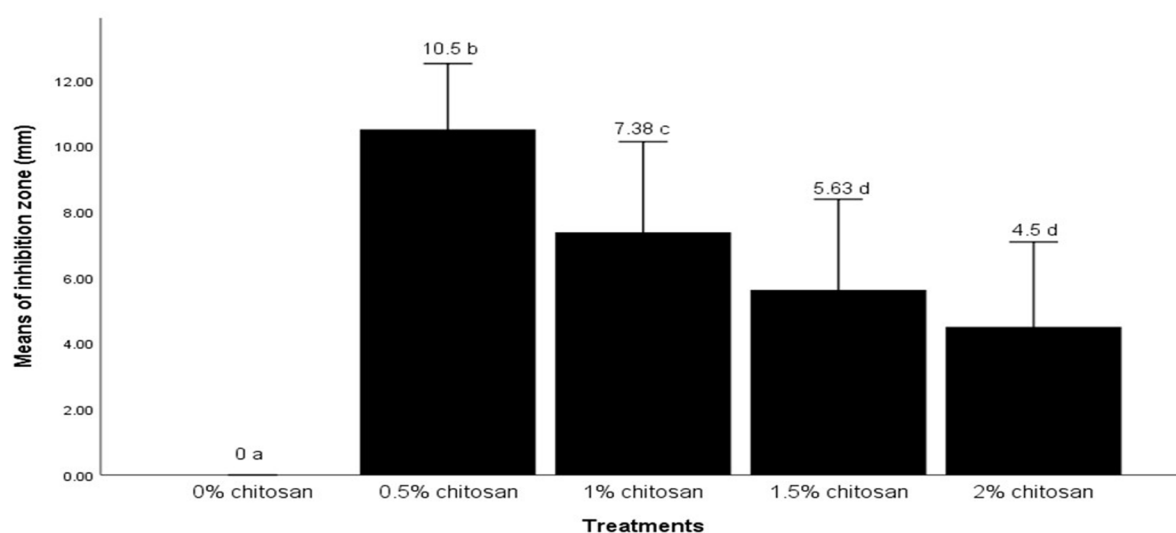


Figure 4. Inhibition zone of chitosan against *Fusarium* sp. Note: Different alphabets show significant differences ($p < 0.05$). The data were expressed as mean \pm standard deviation (SD) of three replications.

Table 3. Mean of water stability of experimental pellets.

Treatments	Mean initial weight \pm SD (g)	Mean final weight \pm SD (g)	Mean water stability \pm SD (%)
0% chitosan	1.39 \pm 0.00	1.14 \pm 0.01	82.33 \pm 0.30 ^a
0.5% chitosan	1.39 \pm 0.00	1.27 \pm 0.01	90.80 \pm 0.20 ^b
1% chitosan	1.39 \pm 0.00	1.35 \pm 0.01	97.00 \pm 0.10 ^c
1.5% chitosan	1.39 \pm 0.00	1.36 \pm 0.01	97.48 \pm 0.08 ^d
2% chitosan	1.39 \pm 0.00	1.37 \pm 0.01	97.75 \pm 0.05 ^d

Note: Different alphabets show significant differences ($p < 0.05$). The data were expressed as mean \pm standard deviation (SD) of three replications.

Bolat *et al.* (2010) and Luthfiyana *et al.* (2022) who respectively reported that the yield of chitosan from mangrove crab shells was 4.65% and 5.82%. These differentiations probably affected several factors such as concentration of NaOH, temperature, time of extraction as well as the environment of each species. The higher concentration of NaOH, the lower of yield chitosan (Luthfiyana *et al.*, 2022). However, in the case of Cuttlefish (*S.pharaonis* sp.), the percentage of yield chitosan in higher NaOH concentration (12.5 M) was higher than 7.5 M of NaOH (Hazeena *et al.*, 2022). These findings suggest that NaOH is not a single factor affecting the yield of chitosan. it depends also on the species of animals. In addition, Bolat *et al.* (2010) stated that species and their environment affect the chitin production from crab shells.

effects on fungal activity and water stability. High levels of ash can interfere with chitosan's ability to bind to fungal cell walls and interfere with their nutrient absorption. This can reduce the effectiveness of chitosan in inhibiting fungal growth (Ke *et al.*, 2021) in lobster feed. Furthermore, some types of minerals in ash, such as calcium and magnesium, can act as nutrients for mold (Lübeck *et al.*, 2022). This can encourage mold growth in lobster feed, especially if the water content is also high. In terms of water stability, high ash content can reduce chitosan's ability to absorb and hold water (Adamczuk *et al.*, 2021). This can cause shrimp feed to dry out and break down more easily, making it more difficult for shrimp to consume. In addition, ash dissolved in water can increase the turbidity (Brito *et al.*, 2021) of cultivation water. This can disrupt plankton photo

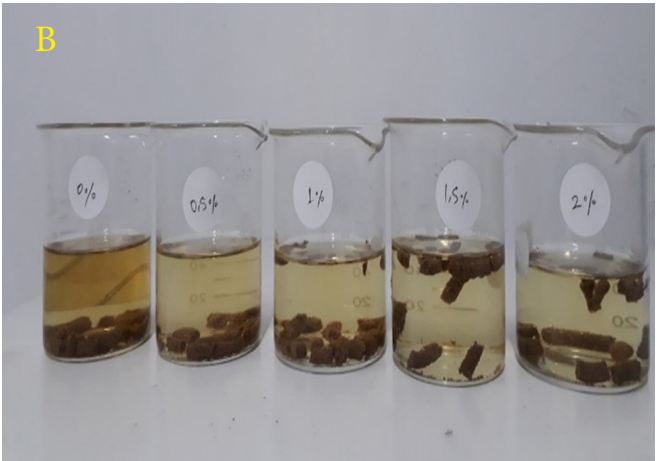
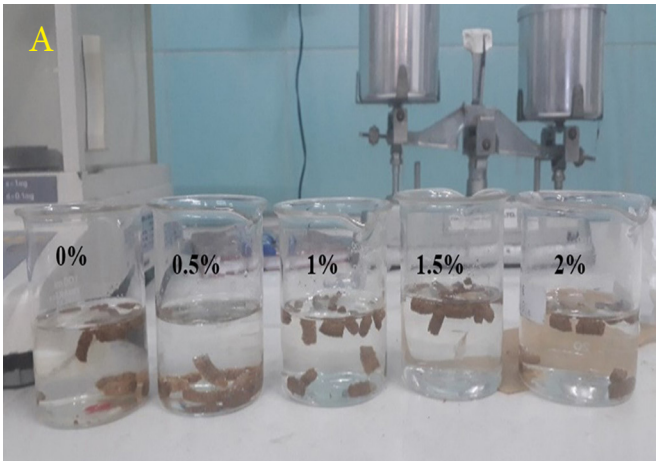


Figure 5. The color of water changing before (A) and after (B) experiment.

The moisture content was $5.94 \pm 0.07\%$, which complied with Protan Laboratory and EFSA standards. This moisture was low because chitosan contains acetyl groups that are hydrophobic or dislike water. The chitosan, therefore, does not bind the water (Cui *et al.*, 2016; Onwuka *et al.*, 2019).

The ash content of chitosan was $36.72 \pm 0.05\%$ which is higher than Protan Laboratory and EFSA standards. The ash content is strongly caused by the concentration of HCl, temperature, and the length of time of demineralization (Luthfiyana *et al.*, 2022). In previous research, the ash content of chitin produced with 6N HCl and temperature 33°C was lower than 2N HCl and 4N HCl. This is because of the higher concentration of HCl, and the higher reactivity rate between the HCl and minerals. Furthermore, the reaction will be faster at a higher temperature (Nugroho *et al.*, 2020).

High ash content in chitosan can have adverse

synthesis and reduce shrimp visibility, which can have negative consequences for their health and growth.

Based on this result, the nitrogen content of chitosan was in accordance with the EFSA standards. This result is in line with the previous research which stated that the mangrove crab shells also have 1.32% of nitrogen content. Sodium hydroxide (NaOH) is one kind of reagent that disrupts the bond of chemicals between chitin and protein (Younes and Rinaudo, 2015).

The degree of deacetylation (DD) is a parameter that highly affects the biological, physicochemical, and mechanical properties of chitosan (Metin *et al.*, 2019). Based on this study, the degree of deacetylation was $96.99 \pm 0.01\%$, which complies with the EFSA standards. Concentration of NaOH and temperature of deacetylation highly affect the degree of deacetylation (Mathaba and Daramola, 2020). Moreover, hydrolysis

of the biopolymer causes a decrease in the molecular weight of chitosan (Younes and Rinaudo, 2015).

The degree of deacetylation (DD) is an important parameter in chitosan which measures the percentage of acetyl groups removed from the chitin chain. Chitosan with high DD has fewer acetyl groups and more free amino groups. This provides several benefits in relation to fungal activity and water stability in shrimp feed. Chitosan with high DD has a stronger ability to bind to fungal cell walls and interfere with their nutrient absorption. This can increase the effectiveness of chitosan in inhibiting fungal growth (Ke et al., 2021) in shrimp or lobster feed. Moreover, chitosan with high DD has been proven to be effective against various types of fungal pathogens that are often found in shrimp feed, including *Aspergillus flavus*, *Fusarium moniliforme*, and *Penicillium* sp. (Ke et al., 2022; Karamchandani et al., 2022; Gong et al., 2024). Regarding water stability, chitosan with high DD has better ability to absorb and retain water (Jin et al., 2017). This can help keep the shrimp or lobster feed moist and prevent it from drying out and falling apart, making it easier for the shrimp or lobster to consume. Furthermore, Chitosan with high DD has a higher absorption capacity for heavy metals and other organic compounds (Hsu et al., 2024) found in cultivation water. This can help improve water quality and reduce water pollution.

The pattern of FTIR vibrations are in accordance with the FTIR spectra of *Portunus pelagicus*, commercial chitosan, and mangrove crab shells conducted by Ahyat et al. (2017), Gharaie et al. (2018), and Luthfiyana et al. (2022), respectively. The SEM-EDX result is the same as the morphology of chitosan from mangrove crab shells reported by other researchers (Liu et al., 2022; Luthfiyana et al., 2022). The data of FTIR and SEM-EDX are strong evidence that chitosan is successfully manufactured.

3.2.2 In vitro assay of anti-fungal activity of chitosan

Fusarium spp. are fungal pathogens responsible for plant diseases and also act as agents of infections in humans and animals. These fungi are ubiquitous and can colonize various organic substances, such as fish and crustacean pellets, due to their remarkable adaptability to diverse environmental conditions (Ekwomadu and Mwanza, 2023). The *Fusarium* colonies observed in this study resemble those of *Fusarium solani*, characterized by their white to cream coloration (Leslie and Summerell, 2006).

Based on *in vitro* assay, chitosan has a significant effect as a fungicidal in lobster pellets, with 0.5%

of chitosan showing the best concentration. This result aligns with previous findings, demonstrating that chitosan and its derivatives effectively inhibit *Rhizoctonia solani*, *Fusarium oxysporum*, *Collectotrichum acutatum*, and *Phytophthora infestans* (Divya et al., 2018), *Collectotrichum gleosporioides* (Wu et al., 2023), *Candida albicans* (Gamil et al., 2024), *Aspergillus niger* (El-Araby et al., 2022), *Alteraria alternata* (Guo et al., 2020), and *Collectotrichum truncatum* (Gowda and Sri-ram, 2023).

The fungicidal effects of chitosan operate through an intracellular mechanism, penetrating pathogenic cells or accumulating on cell walls, membranes, or septa. This process disrupts cell membrane permeability by causing ion exchange, particularly K⁺ or cytoplasmic content loss, resulting in the leakage of cellular components like proteins and nucleic acids, ultimately leading to the breakdown of cell structure (Guo et al., 2020; Ke et al., 2021; Singh et al., 2008). The zone of inhibition was decreased for chitosan levels of 1% or more, which may relate to the incomplete demineralization of our process.

3.2.3 Water Stability of lobster pellets

The quality of lobster diets depends not only on their nutritional composition but also on their physical properties, particularly water stability. Lobster pellets must remain intact to prevent disintegration and the loss of water-soluble nutrients when exposed to water or during consumption. Unlike fast-feeding fish species such as salmon, catfish, and tilapia, which require pellets with short water stability, lobsters need pellets with extended stability due to their slow and selective feeding habits. Using their chelate pereopods, lobsters handle and masticate the feed outside the buccal cavity before ingestion. Consequently, a formulated lobster diet must be well-bound to endure feeding manipulation, reduce feed waste, and maintain water quality (Chouljenko et al., 2024).

Chitosan serves as an effective binder and coating agent to enhance the water stability of lobster pellets. The acetyl groups in chitosan facilitate the formation of hydrogen bonds, which stabilize the crystalline structure of the pellets and reduce nutrient leaching. Moreover, chitosan, with higher degree of deacetylation, exhibits even greater resistance to fracture (Cui et al., 2016). The resulted water stability in this research align with previous research, which demonstrated that chitosan-containing pellets maintained a highly stable size distribution during water immersion tests (Volpe et al., 2012).

4. Conclusion

Chitosan morphology was identified as an irregular shape with striated surface textures. The yield of chitosan was $5.9 \pm 0.01\%$ of the total shell mass, with $96.99\% \pm 0.01$ degree of deacetylation (DD). The resulting product contained $5.94 \pm 0.07\%$ moisture, $36.72 \pm 0.05\%$ ash and $2.73 \pm 0.08\%$ nitrogen. . This research has highlighted two major roles of chitosan in lobster feeds; at 0.5% inclusion, chitosan optimally inhibits fungi (*Fusarium* sp.), while higher inclusion (1.5%) was required to optimize water stability. Chitosan from lobster shells has strong antimicrobial properties, as well as effectively binding pellets and reducing nutrient losses into the water. These properties are expected to maintain pellet integrity and microbial status for increased nutrient delivery and health of farmed lobsters. In addition, this research demonstrated an effective circular use of existing waste products that can increase sustainability of the lobster supply chain. It is likely that mold inhibition and water holding capacity of chitosan can be further improved through optimized demineralization, while future research should explore long-term dietary effects, digestibility, and growth performance in lobsters to optimize its commercial viability in aquaculture. By integrating waste valorization with functional feed improvements, this study supports circular economy principles in seafood production.

Acknowledgment

The authors would like to thank the center of research and community development of Islamic State University of Mataram (LPPM UIN Mataram) and Faculty of Education (FTK UIN Mataram) that supported the funding of this research.

Authors' Contribution

All authors made significant contributions to the manuscript. MI and Mg were responsible for data collection and drafting the manuscript. AH and Mk contributed to data analysis and figure design. NP, HM, BP, CJ, and LN were involved in conceptualizing the main idea and providing critical revisions to the article.

Conflict of Interest

The authors declare that they have no competing interests.

Declaration of Artificial Intelligence (AI)

The author(s) acknowledge the use of ChatGPT

for language refinement in preparing this manuscript. All AI-generated content was rigorously reviewed, edited, and validated to ensure accuracy and originality. Full responsibility for the manuscript's final content rests with the author(s). To ensure transparency and support the review process, a comprehensive delineation of the tool's application is furnished in the "Introduction" or "Materials and Methods" section of this manuscript in compliance with the publisher's ethical guidelines.

Funding Information

This research was fully supported by Universitas Islam Negeri Mataram with grant number: 56/Un.12/P3I-LP2M/PP.00.9/02/2022.

References

- Abdel-Razek, N. (2019). Antimicrobial activities of chitosan nanoparticles against pathogenic microorganisms in Nile tilapia, *Oreochromis niloticus*. *Aquaculture international*, 27(5):1315-1330.
- Adamczuk, A., Kercheva, M., Hristova, M., & Jozefaciuk, G. (2021). Impact of chitosan on water stability and wettability of soils. *Materials*, 14(24):1-12.
- Ahyat, N. M., Mohamad, F., Ahmad, A., & Azmi, A. A. (2017). Chitin and chitosan extraction from *Portunus pelagicus*. *Malaysian Journal of Analytical Sciences*, 21(4):770-777.
- Aly, S. M., Eissa, A. E., Abdel-Razek, N., & El-Ramlawy, A. O. (2023). The antibacterial activity and immunomodulatory effect of naturally synthesized chitosan and silver nanoparticles against *Pseudomonas fluorescence* infection in Nile tilapia (*Oreochromis Niloticus*): An in vivo study. *Fish & shellfish immunology*, 135(1):108628-108628.
- Amine, R., Tarek, C., Hassane, E., Noureddine, E. H., & Khadija, O. (2021). Chemical proprieties of biopolymers (chitin/chitosan) and their synergic effects with endophytic *Bacillus* species: Unlimited applications in agriculture. *Molecules*, 26(4):1-26.
- Anas, A., Philip, R., & Singh, I. S. B. (2008). Chitosan as a wall material for a microencapsulated delivery system for *Macrobrachium rosenbergii* (de Man) larvae. *Aquaculture research*, 39(8):885-890.
- Azmin, N., Nasir, M., & Hartati. (2019). Utilization of shrimp shell (*Penaeus monodon*) for making chitosan as a natural meat preservative. *Oryza Jurnal Pendidikan Biologi* 8(1):9-15.

- Bastiaens, L., Soetemans, L., D'Hondt, E., & Elst, K. (2020). Sources of chitin and chitosan and their isolation. In L. A. M. V. D. Broek & C. G. Boeriu (Eds.), *Chitin and chitosan: Properties and applications*. (pp. 1-28). UK: John Wiley & Sons.
- Betchem, G., Johnson, N. A. N., & Wang, Y. (2019). The application of chitosan in the control of post-harvest diseases: A review. *Journal of plant diseases and protection*, 126(6):495-507.
- Bolat, Y., Bilgin, S., Gunlu, A., Izci, L., Koca, S. B., Cetinkaya, S., & Koca, H. U. (2010). Chitin-chitosan yield of freshwater crab (*Potamon potamios*, Olivier 1804) shell. *Pakistan veterinary journal*, 30(4):227-231.
- Brito, D. Q., Santos, L. H. G., Passos, C. J. S., & Oliveira-Filho, E. C. (2021). Short-term effects of wild-fire ash on water quality parameters: A laboratory approach. *Bulletin of environmental contamination and toxicology*, 107(3):500-505.
- Cha, S.-H., Lee, J.-S., Song, C.-B., Lee, K.-J., & Jeon, Y.-J. (2008). Effects of chitosan-coated diet on improving water quality and innate immunity in the olive flounder, *Paralichthys olivaceus*. *Aquaculture*, 278(1):110-118.
- Chaudhari, A. K., Das, S., Dwivedi, A., & Dubey, N. K. (2023). Application of chitosan and other biopolymers based edible coatings containing essential oils as green and innovative strategy for preservation of perishable food products: A review. *International journal of biological macromolecules*, 253(8):127688-127688.
- Chen, G., Yin, B., Liu, H., Tan, B., Dong, X., Yang, Q., Chi, S., & Zhang, S. (2021). Supplementing chitosan oligosaccharide positively affects hybrid grouper (*Epinephelus fuscoguttatus* ♀ × *E. lanceolatus* ♂) fed dietary fish meal replacement with cottonseed protein concentrate: Effects on growth, gut microbiota, antioxidant function and immune response. *Frontiers in Marine Science*, 8(1):1-18.
- Chouhan, D., & Mandal, P. (2021). Applications of chitosan and chitosan based metallic nanoparticles in agrosocieties-a review. *International journal of biological macromolecules*, 166(1):1554-1569.
- Chouljenko, A., Mirtalebi, S., Hopper, S., Santos, F., Bolton, G., Bailey, C., & Christyn, B. (2024). Combining fish and crustacean byproducts as primary ingredients in pelleted aquafeed: The effect of byproduct type on pellet physical properties. *Aquaculture research*, 2024(1):1-10.
- Confederat, L. G., Tuchilus, C. G., Dragan, M., Sha'at, M., & Dragostin, O. M. (2021). Preparation and antimicrobial activity of chitosan and its derivatives: A concise review. *Molecules*, 26(12):1-17.
- Cui, J., Yu, Z., & Lau, D. (2016). Effect of acetyl group on mechanical properties of chitin/chitosan nanocrystal: A molecular dynamics study. *International journal of molecular sciences*, 17(1):61-61.
- Díaz-montes, E., & Castro-muñoz, R. (2021). Trends in chitosan as a primary biopolymer for functional films and coatings manufacture for food and natural products. *Polymers*, 13(5):1-28.
- Divya, K., Smitha, V., & Jisha, M. S. (2018). Antifungal, antioxidant and cytotoxic activities of chitosan nanoparticles and its use as an edible coating on vegetables. *International journal of biological macromolecules*, 15(114):572-577.
- Elbahnaswy, S., Elshopakey, G. E., Ibrahim, I., & Habotta, O. A. (2021). Potential role of dietary chitosan nanoparticles against immunosuppression, inflammation, oxidative stress, and histopathological alterations induced by Pendimethalin toxicity in Nile tilapia. *Fish & shellfish immunology*, 118(1):270-282.
- Ekwomadu, T. I., & Mwanza, M. (2023). Fusarium fungi pathogens, identification, adverse effects, disease management, and global food security: A review of the latest research. *Agriculture*, 13(9):1-20.
- El-Araby, A., El Ghadraoui, L., & Errachidi, F. (2022). Usage of biological chitosan against the contamination of post-harvest treatment of strawberries by *Aspergillus niger*. *Frontiers in sustainable food systems*, 6(1):1-15.
- Fadl, S. E., El-Gammal, G. A., Abdo, W. S., Barakat, M., Sakr, O. A., Nassef, E., Gad, D. M., & El-Sheshtawy, H. S. (2020). Evaluation of dietary chitosan effects on growth performance, immunity, body composition and histopathology of Nile tilapia (*Oreochromis niloticus*) as well as the resistance to *Streptococcus agalactiae* infection. *Aquaculture research*, 51(3):1120-1132.
- Gamil, Y., Hamed, M. G., Elsayed, M., Essawy, A., Medhat, S., Zayed, S. O., & Ismail, R. M. (2024). The anti-fungal effect of miconazole and miconazole-loaded chitosan nanoparticles gels in

- diabetic patients with oral candidiasis-randomized control clinical trial and microbiological analysis. *BMC oral health*, 24(1):196-196.
- Gharaie, S. S., Habibi, S., & Nazockdast, H. (2018). Fabrication and characterization of chitosan/gelatin/thermoplastic polyurethane blend nanofibers. *Journal of Textiles and Fibrous Materials*, 1(1):1-8.
- Gong, W., Sun, Y., Tu, T., Huang, J., Zhu, C., Zhang, J., Salah, M., Zhao, L., Xia, X., & Wang, Y. (2024). Chitosan inhibits *penicillium expansum* possibly by binding to DNA and triggering apoptosis. *International Journal of Biological Molecule*, 259(1):1-9.
- Gowda, S., & Sriram, S. (2023). Green synthesis of chitosan silver nanocomposites and their antifungal activity against *Colletotrichum truncatum* causing anthracnose in chillies. *Plant Nano Biology*, 5(3):1-11.
- Goy, R. C., De Britto, D., & Assis, O. B. G. (2009). A review of the antimicrobial activity of chitosan. *Polímeros, ciência e tecnologia*, 19(3):241-247.
- Guo, H., Qiao, B., Ji, X., Wang, X., & Zhu, E. (2020). Antifungal activity and possible mechanisms of submicron chitosan dispersions against *alteraria alternata*. *Postharvest biology and technology*, 161(3):1-8.
- Hazeena, S. H., Hou, C. Y., Zeng, J. H., Li, B. H., Lin, T. C., Liu, C. S., Chang, C. I., Hsieh, S. L., & Shih, M. K. (2022). Extraction optimization and structural characteristics of chitosan from cuttlefish (*S. pharaonis* sp.) bone. *Materials*, 15(22):1-15.
- Hsu, C.-Y., Ajaj, Y., Mahmoud, Z. H., Kamil Ghadir, G., Khalid Alani, Z., Hussein, M. M., Abed Hussein, S., Morad Karim, M., Al-khalidi, A., Abbas, J. K., Hussein Kareem, A., & Kianfar, E. (2024). Adsorption of heavy metal ions use chitosan/graphene nanocomposites: A review study. *Results in Chemistry*, 7(1):1-24.
- Ibrahim, D., Neamat-Allah, A. N. F., Ibrahim, S. M., Eissa, H. M., Fawzey, M. M., Mostafa, D. I. A., El-Kader, S. A. A., Khater, S. I., & Khater, S. I. (2021). Dual effect of selenium loaded chitosan nanoparticles on growth, antioxidant, immune related genes expression, transcriptomics modulation of caspase 1, cytochrome P450 and heat shock protein and *Aeromonas hydrophila* resistance of Nile tilapia (*Oreochromis niloticus*). *Fish & shellfish immunology*, 110(1):91-99.
- Ihsan, M., Priyambodo, B., & Muliasari, H. (2020). Training on making gel feed based on local ingredients as alternative feed for lobster cultivation on Lombok Island. *Transformasi Jurnal Pengabdian Masyarakat*, 16(1):1-11.
- Jin, Q., Yu, H., Wang, X., Li, K., & Li, P. (2017). Effect of the molecular weight of water-soluble chitosan on its fat-/cholesterol-binding capacities and inhibitory activities to pancreatic lipase. *PeerJ*, 5(1):1-22.
- Jones, C. M., Anh, T. L., & Priyambodo, B. (2019). Lobster aquaculture development in Vietnam and Indonesia. In E. V. Radhakrisnan, B. F. Phillips, & G. Achamveetil (Eds.), *Lobsters: Biology, fisheries and aquaculture*. Singapore: Springer Nature Singapore Pte.Ltd.
- Karamchandani, B. M., Chakraborty, S., Dalvi, S. G., & Satpute, S. K. (2022). Chitosan and its derivatives: Promising biomaterial in averting fungal diseases of sugarcane and other crops. *Journal of basic microbiology*, 62(5):533-554.
- Ke, C.-L., Deng, F.-S., Chuang, C.-Y., & Lin, C.-H. (2021). Antimicrobial actions and applications of chitosan. *Polymers*, 13(6):1-21.
- Ke, Y., Ding, B., Zhang, M., Dong, T., Fu, Y., Lv, Q., Ding, W., & Wang, X. (2022). Study on inhibitory activity and mechanism of chitosan oligosaccharides on *Aspergillus flavus* and *Aspergillus fumigatus*. *Carbohydrate Polymers*, 275(1):1-8.
- Kumar, B.T.N., Thakur, N., Sharma, C., Shanthanagouda, A. H., Taygi, A., & Singh, A. (2022). Effect of dietary chitosan nanoparticles on immune response and disease resistance against *Aeromonas Hydrophila* infection in tropical herbivore fish (Rohu, *Labeo rohita*). *Aquaculture international*, 30(5):2439-2452.
- Kurniawidi, D. W., Alaa, S., Nurhaliza, E., Safitri, D. O., Rahayu, S., Ali, M., & Amin, M. (2022). Synthesis and characterization of nano chitosan from vannamei shrimp shell (*Litopenaeus vannamei*). *Jurnal Ilmiah Perikanan dan Kelautan*, 14(2):380-387.
- Leslie, J. F., & Summerell, B. A. (2006). *Fusarium laboratory manual* (1st ed.). Blackwell Pub.
- Li, J., & Zhuang, S. (2020). Antibacterial activity of chitosan and its derivatives and their interaction

- mechanism with bacteria: Current state and perspectives. *European polymer journal*, 138(1):1-12.
- Liu, J., Xu, W., Liu, Y., Wang, Y., Zhang, J., Wang, Z., Mai, K., & Ai, Q. (2022). Effects of chitosan-coated microdiet on dietary physical properties, growth performance, digestive enzyme activities, antioxidant capacity, and inflammation response of large yellow croaker (*Larimichthys crocea*) larvae. *Aquaculture nutrition*, 2022(1):1-11.
- Lübeck, M., & Lübeck, P. S. (2022). Fungal cell factories for efficient and sustainable production of proteins and peptides. *Microorganisms*, 10(4):1-24.
- Luthfiyana, N., Bija, S., Nugraeni, C. D., Lembang, M. S., Anwar, E., Laksmiawati, D. R., & Ratrinia, P. W. (2022). Characteristics and antibacterial activity of chitosan nanoparticles from mangrove crab shell (*Scylla* sp.) in Tarakan Waters, North Kalimantan, Indonesia. *Biodiversitas*, 23(8):4018-4025.
- Masruriati, E., Ariyanti, Imadahidayah, T., & Sulistianingsih, E. N. (2020). Utilization of chitosan from feather clam shells (*Anadara antiquate*) as a preservative for stingrays (*Dasyatis* sp.) and white shrimp (*Litopenaeus vannamei*). *Riset Informasi Kesehatan*, 9(1):12-21.
- Mathaba, M., & Daramola, M. O. (2020). Effect of chitosan's degree of deacetylation on the performance of PES membrane infused with chitosan during AMD treatment. *Membranes*, 10(3):1-16.
- Metin, C., Alparslan, Y., Baygar, T., & Baygar, T. (2019). Physicochemical, microstructural and thermal characterization of chitosan from blue crab shell waste and its bioactivity characteristics. *Journal of polymers and the environment*, 27(11):2552-2561.
- Naiel, M. A. E., Ismael, N. E. M., Abd El-hameed, S. A. A., & Amer, M. S. (2020). The antioxidative and immunity roles of chitosan nanoparticle and vitamin C-supplemented diets against imidacloprid toxicity on *Oreochromis niloticus*. *Aquaculture*, 523(1):1-11.
- Nugroho, I. L., Masithah, E. D., & Pursetyo, K. T. (2020). The effect of hydrochloric acid concentration and temperature demineralization on characteristics of chitin from penshell (*Atrina pectinata*). *IOP conference series. Earth and environmental science*, 441(1):1-7.
- Onwuka, J. C., Agbaji, E. B., Ajibola, V. O., & Okibe, F. G. (2019). Thermodynamic pathway of ligno-cellulosic acetylation process. *BMC chemistry*, 13(1):1-11.
- Picos-Corrales, L. A., Morales-Burgos, A. M., Ruélas-Leyva, J. P., Crini, G., García-Armenta, E., Jimenez-Lam, S. A., Ayón-Reyna, L. E., Rocha-Alonzo, F., Calderón-Zamora, L., Osuna-Martínez, U., Calderón-Castro, A., De-Paz-Arroyo, G., & Inzunza-Camacho, L. N. (2023). Chitosan as an outstanding polysaccharide improving health-commodities of humans and environmental protection. *Polymers*, 15(3):1-27.
- Román-Doval, R., Torres-Arellanes, S. P., Tenorio-Barajas, A. Y., Gómez-Sánchez, A., & Valencia-Lazcano, A. A. (2023). Chitosan: Properties and its application in agriculture in context of molecular weight. *Polymers*, 15(13):1-26.
- Romanazzi, G., Feliziani, E., & Sivakumar, D. (2018). Chitosan, a biopolymer with triple action on post-harvest decay of fruit and vegetables: Eliciting, antimicrobial and film-forming properties. *Frontiers in microbiology*, 9(1):1-9.
- Romanazzi, G., & Moumni, M. (2022). Chitosan and other edible coatings to extend shelf life, manage postharvest decay, and reduce loss and waste of fresh fruits and vegetables. *Current opinion in biotechnology*, 78(1):1-9.
- Salam, M. A., Rahman, M. A., Paul, S. I., Islam, F., Barman, A. K., Rahman, Z., Shaha, D. C., Rahman, M. M., & Islam, T. (2021). Dietary chitosan promotes the growth, biochemical composition, gut microbiota, hematological parameters and internal organ morphology of juvenile *Barbonymus gonionotus*. *PloS one*, 16(11):1-23.
- Saputra, D., Ula, F. R., Fadhila, A. B. N., Sijabat, Y. Y., Romadoni, A. A., & Windarto, S. (2022). Nano-chitosan spray as a preservative and food security of fishery products in the middle of the Covid-19 pandemic. *Jurnal Ilmiah Perikanan dan Kelautan*, 14(1):71-82.
- Shahbaz, U., Basharat, S., Javed, U., Bibi, A., & Yu, X. B. (2023). Chitosan: A multipurpose polymer in food industry. *Polymer bulletin*, 80(4):3547-3569.
- Shi, F., Qiu, X., Nie, L., Hu, L., Babu V, S., Lin, Q., Zhang, Y., Chen, L., Li, J., Lin, L., & Qin, Z. (2020). Effects of oligochitosan on the growth, immune responses and gut microbes of Tilapia

(*Oreochromis niloticus*). *Fish & shellfish immunology*, 106(1):563-573.

- Shrestha, R., Thenissery, A., Khupse, R., & Rajashekar, G. (2023). Strategies for the preparation of chitosan derivatives for antimicrobial, drug delivery, and agricultural applications: A review. *Molecules*, 28(22):1-39.
- Singh, T., Vesentini, D., Singh, A. P., & Daniel, G. (2008). Effect of chitosan on physiological, morphological, and ultrastructural characteristics of wood-degrading fungi. *International Biodeterioration & Biodegradation*, 62(2):116-124.
- Statista. (2024). Volume of lobsters exported from Indonesia from 2014 to 2022.
- Teixeira-Santos, R., Lima, M., Gomes, L. C., & Mergulhão, F. J. (2021). Antimicrobial coatings based on chitosan to prevent implant-associated infections: A systematic review. *iScience*, 24(12):1-23.
- Volpe, M. G., Varricchio, E., Coccia, E., Santagata, G., Di Stasio, M., Malinconico, M., & Paolucci, M. (2012). Manufacturing pellets with different binders: Effect on water stability and feeding response in juvenile *Cherax albidus*. *Aquaculture*, 324(12):104-110.
- Wang, R., Li, X., Tang, J., Liu, J., Yin, H., Li, R., & Ye, S. (2023). Dietary effect chitosan nanoparticles on growth performance, immunity and resistance against *Vibrio splendidus* in the sea cucumber *Apostichopus japonicas*. *Aquaculture reports*, 30(1):1-7.
- Wu, J., Chang, J., Liu, J., Huang, J., Song, Z., Xie, X., Wei, L., Xu, J., Huang, S., Cheng, D., Li, Y., Xu, H., & Zhang, Z. (2023). Chitosan-based nanopesticides enhanced anti-fungal activity against strawberry anthracnose as “sugar-coated bombs”. *International Journal of Biological Macromolecules*, 253(36):126947-126947.
- Xu, H., Wang, X., Liang, Q., Xu, R., Liu, J., & Yu, D. (2023). Dietary chitosan moderates the growth rate, antioxidant activity, immunity, intestinal morphology and resistance against *Aeromonas hydrophila* of juvenile hybrid sturgeon (*Acipenser baerii*♀ × *Acipenser schrenckii*♂). *International journal of biological macromolecules*, 224(1):1012-1024.
- Younes, I., & Rinaudo, M. (2015). Chitin and chitosan preparation from marine sources. Structure, properties and applications. *Marine drugs*, 13(3):1133-1174.
- Zeng, A., Wang, Y., Li, D., Guo, J., & Chen, Q. (2021). Preparation and antibacterial properties of polycaprolactone/quaternized chitosan blends. *Chinese journal of chemical engineering*, 32(4):462-471.